



Distributed in the Interest
of Product Development

VANDERBILT

Technical Data

No. 1240
Rubber Department

SONGNOX[®] 1010

for use in Natural Rubber Latex

Accelerated heat aging is one of the best gauges of the long-term performance of a finished latex article. The use of **SONGNOX 1010** in a natural rubber latex compound significantly improves its heat aging properties and provides protection to the physical properties during the use and storage of the end-product. It is FDA-listed under 21 CFR 178.2010. Finally, the use of **SONGNOX 1010** provides superior retention of physical properties when compared to a common latex antioxidant*.

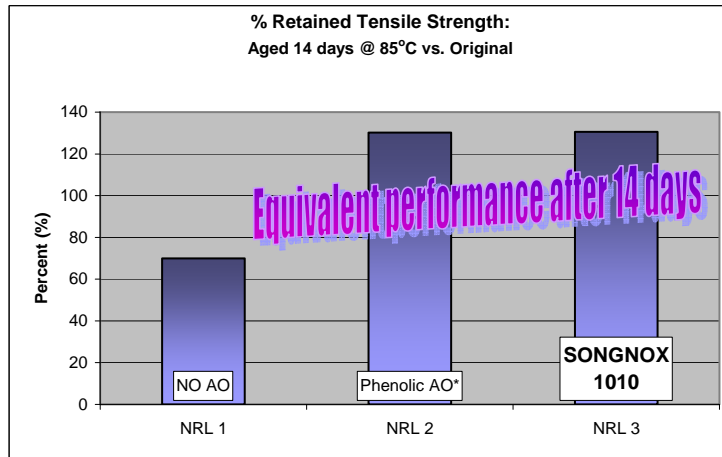


Figure 1: Retained Tensile Strength, Aged 14 days at 85°C

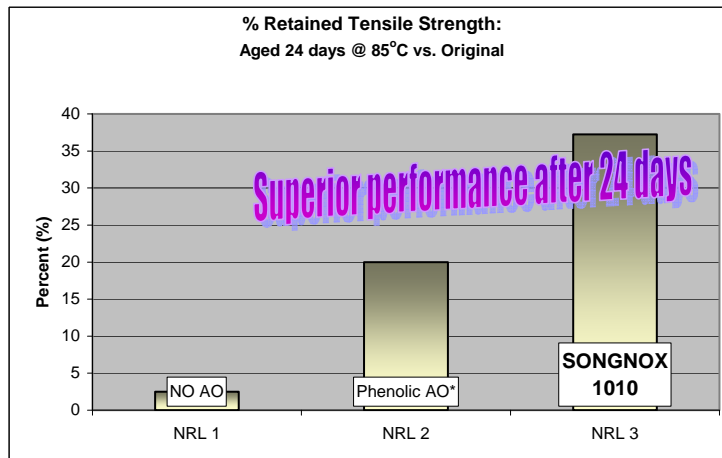


Figure 2: Retained Tensile Strength, Aged 24 days at 85°C

R.T. Vanderbilt Company, Inc., 30 Winfield Street, P.O. Box 5150, Norwalk, CT 06856-5150
Telephone: (203) 853-1400 - Fax: (203) 853-1452 - Web Site: www.rtvanderbilt.com

Before using, read, understand and comply with the information and precautions in the Material Safety Data Sheets, label and other product literature. The information presented herein, while not guaranteed, was prepared by technical personnel and, to the best of our knowledge and belief, is true and accurate as of the date hereof. No warranty, representation or guarantee, express or implied, is made regarding accuracy, performance, stability, reliability or use. This information is not intended to be all-inclusive, because the manner and conditions of use, handling, storage and other factors may involve other or additional safety or performance considerations. The user is responsible for determining the suitability of any material for a specific purpose and for adopting such safety precautions as may be required. R.T. Vanderbilt Company, Inc. does not warrant the results to be obtained in using any material, and disclaims all liability with respect to the use, handling or further processing of any such material. No suggestion for use is intended as, and nothing herein shall be construed as, a recommendation to infringe any existing patent, trademark or copyright or to violate any federal, state or local law or regulation.

The following test recipe can be used as a starting point when compounding with this antioxidant system.

INGREDIENTS	COMPOUNDS (phr)		
	NRL1	NRL2	NRL3
High-Ammonia Natural Rubber Latex	100.0	100.0	100.0
Potassium hydroxide (10%)	0.5	0.5	0.5
DARVAN® WAQ surfactant	0.5	0.5	0.5
ZINC OXIDE Dispersion	0.5	0.5	0.5
Sulfur dispersion	1.0	1.0	1.0
BUTYL ZIMATE® Slurry	1.5	1.5	1.5
DARVAN® SMO surfactant	0.5	0.5	0.5
SONGNOX 1010 antioxidant	---	---	1.0
Phenolic antioxidant*	---	1.0	---
Totals	104.5	105.5	105.5

RESULTS	COMPOUNDS		
	NRL1	NRL2	NRL3
<i>Original Physical Properties, Cured 30 minutes @ 100°C</i>			
300% Modulus, MPa	1.6	1.5	1.7
Tensile, MPa	16.8	21.0	18.0
Elongation,%	641.4	703.1	643.1
<i>Physical Properties After Aging 14 days @ 85°C</i>			
300% Modulus, MPa	2.1	2.3	2.3
Tensile, MPa	11.8	27.3	26.6
Elongation,%	482.6	543.3	531.0
<i>Physical Properties After Aging 24 days @ 85°C</i>			
300% Modulus, MPa	---	1.6	1.5
Tensile, MPa	0.4	4.2	6.7
Elongation, %	61.9	441.0	530.7

SONGNOX Antioxidant is a registered trademark of Songwon Industrial Co., Ltd.

DARVAN® Dispersants and ZIMATE® Accelerators are registered trademarks of R.T. Vanderbilt Company, Inc.

*Phenolic Antioxidant = Butylated reaction product of p-cresol and dicyclopentadiene